




鞍钢股份有限公司
Angang Steel Company Limited

产品质量证明书

INSPECTION CERTIFICATE



中国鞍山市铁东区团结街42号 邮编 114002
No.42 Tuanjie Street Tiedong District 114002
Anshan. P. R. China
Tel 0086-8008900858 Fax 0086-0412-6728486

制造厂: 鞍钢股份有限公司鲅鱼圈中厚板厂3800线
Manufacturer: Bayuquan Heavy Plate Plant 3800 Line of AnSteel

正页 第 2 页, 共 3 页

订货单位 Buyer	鞍钢集团国际经济贸易有限公司	产品名称 Product	中厚板	合同编号 Contract No.	C2450692003	证明书编号 Certificate No.	CJ2405150071
收货单位 Consignee	鞍钢股份有限公司 (外贸出口)	客户名称 Customer	鞍钢集团国际经济贸易有限公司			交货状态 Delivery Condition	热轧
标准 Specification	ASTM A36/A36M	许可证编号 License No.					
钢牌号 Grade	A36	发货日期 Date of Delivery	20240515	计重方式 Weight Mode	理论重量 Theory		

序号 No.	物料号 Pack No.	熔炼号 Heat No.	规格(mm) Dimensions mm.	重量(kg) Weight	件数 Pcs.	化学成分 Chemical Composition (%)														冷弯Bend			
						*1	C	Si	Mn	P	S	Cev									试样描述 *2	α= 180 ° d=3a	试批号 Batch No.
							10 -2	10 -2	10 -2	10 -3	10 -3	10 -2											
9	S45132581000	24LD2721	12*2440*12000	2758	1	0	16	19	90	19	7	32								T111	合格	4P6032765400	
10	S45132582000	24LD2721	12*2440*12000	2758	1	0	16	19	90	19	7	32								T111	合格	4P6032765400	
11	S45132591000	24LD2721	12*2440*12000	2758	1	0	16	19	90	19	7	32								T111	合格	4P6032765500	
12	S45132601000	24LD2721	12*2440*12000	2758	1	0	16	19	90	19	7	32								T111	合格	4P6032765400	
13	S45132602000	24LD2721	12*2440*12000	2758	1	0	16	19	90	19	7	32								T111	合格	4P6032765400	
14	S45132631000	24LD2721	12*2440*12000	2758	1	0	16	19	90	19	7	32								T111	合格	4P6032765400	
15	S45132632000	24LD2721	12*2440*12000	2758	1	0	16	19	90	19	7	32								T111	合格	4P6032765400	
16	S45132641000	24LD2721	12*2440*12000	2758	1	0	16	19	90	19	7	32								T111	合格	4P6032765400	
合计Total				22064	8																		


序号 No.	物料号 Pack No.	拉伸Tension						冲击Charpy								硬度Hardness				厚度方向性能(Z)											
		试样描述 p&d *2	屈服 Y.S. Rp0.2 MPa	抗拉 T.S. MPa	伸长率 El %	收缩率 Sh %	屈强比 Y.S./ T.S. %	试批号 Batch No.	试样描述 p&d *2	温度 C°	10*10*55mm J				试批号 Batch No.	试样描述 p&d *2					试批号 Batch No.	试样描述 p&d *2	1	2	3	Ave	试批号 Batch No.				
											KV2						纤维率 SA %											1	2	3	Ave
											1	2	3	Ave			1	2	3	Ave								1	2	3	Ave
9	S45132581000	T131	301	460	47.5		0.65	4P1078108200	T216	20	174	165	173	171					4P7063460100												
10	S45132582000	T131	301	460	47.5		0.65	4P1078108200	T216	20	174	165	173	171					4P7063460100												
11	S45132591000	T131	318	465	48		0.68	4P1078108300	T216	20	182	169	158	170					4P7063460200												
12	S45132601000	T131	301	460	47.5		0.65	4P1078108200	T216	20	174	165	173	171					4P7063460100												
13	S45132602000	T131	301	460	47.5		0.65	4P1078108200	T216	20	174	165	173	171					4P7063460100												
14	S45132631000	T131	301	460	47.5		0.65	4P1078108200	T216	20	174	165	173	171					4P7063460100												
15	S45132632000	T131	301	460	47.5		0.65	4P1078108200	T216	20	174	165	173	171					4P7063460100												
16	S45132641000	T131	301	460	47.5		0.65	4P1078108200	T216	20	174	165	173	171					4P7063460100												

探伤NDT	标准Standard :	级别Class :	结果Result :
-------	--------------	-----------	------------

注释 Notes: *1化学成分: 0.熔炼分析 Heat Analysis; 1.产品分析 Product Analysis; *2试样描述: 大样位置-T头部Head、B尾部Tail + 试验方向-1横向 Transverse、2.纵向 Longitudinal、3.Z向 + 取样位置- 1.板宽1/4、2.板宽2/3、3.板边0.4角部 + 厚度方向位置-1、原厚、2、表面下2mm、3、厚度1/4、4、厚度1/2、5、保留一个轧制面、6、表面下小于2mm、7、厚度1/3 + 试样热处理前后区分-0.交货态 Delivery Condition、1.模拟焊后 PWHT、2.最大模拟焊后热处理 Max PWHT、3.最小模拟焊后热处理 Min PWHT

备注 Remarks: 上述元素仅列出参与复合公式的有意添加元素, 但复合元素结果是严格按公式计算得出。The above elements only list the intentionally added elements that participate in the composite formula, but the composite element results are strictly calculated according to the formula.

说明 Description: 本产品已按上述标准制造和检验, 其结果符合要求。特此证明。贵方如查询有问题, 请与我公司联系。
We hereby certify that material described herein has been manufactured and tested with satisfactory results in accordance with requirements of the above material specification. If you have any questions, please contact our company.

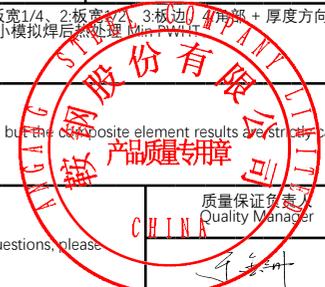

质量保证金
Quality Manager
CHINA

监理
Surveyor